

PHOTOACTIVITY OF TERNARY LEAD–GROUP IVB OXIDES FOR HYDROGEN AND OXYGEN EVOLUTION

Akihiko KUDO ⁺, Menahem STEINBERG ⁺⁺, Allen J. BARD, Alan CAMPION, Marye Anne FOX, Thomas E. MALLOW, Stephen E. WEBBER and John M. WHITE ^{*}

Department of Chemistry, University of Texas, Austin, Texas 78712, USA.

Received 3 January 1990; accepted 5 March 1990

Photocatalysis, photocatalytic activity, PbCrO₄, PbMoO₄, PbWO₄, hydrogen evolution, oxygen evolution, aqueous solutions, ternary lead Group IVB oxides.

The relative photocatalytic activity of a series of lead-IVB group oxides (PbCrO₄, PbMoO₄, and PbWO₄) was studied for hydrogen evolution from aqueous methanol solution and for oxygen evolution from aqueous silver nitrate solution. Among the compounds, only PbMoO₄ and platinized PbMoO₄ powders acted as photocatalysts for oxygen and hydrogen evolution reactions from aqueous solutions, with an activity for oxygen evolution on PbMoO₄ comparable to that observed on TiO₂.

1. Introduction

From the earliest studies of photoelectrochemical (PEC) reactions on semiconductor electrodes and in particle suspensions, new materials have been sought as photocatalysts [1]. Oxides, such as TiO₂, have been of particular interest, since they show high stability under irradiation and are photocatalytically active for many reactions, including the oxidation of organic materials and oxygen evolution. For example, a number of binary [2] and ternary [3] oxides were investigated as photoelectrodes.

Lead oxides are known to be semiconductors [4–6] and a study of the photoelectrochemical behavior of an oxidized Pb surface [2] attributed the anodic photocurrents observed to a PbO layer that was, at least partially, oxidized to higher oxides under irradiation. Although photoelectrochemical studies of lead oxides have been used to characterize anodic films on Pb electrodes [7–9], no

⁺ Present address: The Graduate School at Nagatsuta, Tokyo Institute of Technology, 4259 Nagatsuta, Midori-ku, Yokohama 227, Japan.

⁺⁺ Permanent address: Department of Inorganic Chemistry, The Hebrew University, Jerusalem 91904, Israel.

reports have been published in the photocatalytic activity of lead oxides for oxygen or hydrogen evolution, probably because they are unstable under irradiation in aqueous solution. However, stabilization of the lead oxide structure could occur when it is incorporated into the lattice to form a ternary oxide. For example, the oxides $\text{PbFe}_{12}\text{O}_{19}$ and $\text{Pb}_2\text{Ti}_{1.5}\text{W}_{0.5}\text{O}_{6.5}$ were investigated as photoanodes and were reported to be stable in some electrolytes [3].

In this study, the photocatalytic activity of particulate suspensions of the ternary lead oxides PbCrO_4 , PbMoO_4 , and PbWO_4 is described. Hydrogen evolution from aqueous methanol and oxygen evolution from aqueous silver nitrate solution are reported.

2. Experimental

PbCrO_4 (Mallinckrodt Chemical), PbMoO_4 (Morton Thiokol Inc.), PbWO_4 (Alfa Products), PbO (Johnson Matthey), MoO_3 (Aldrich Chemical), and TiO_2 (MCB) powders were used. The crystal structures were confirmed by X-ray diffraction (Philips, Cu K_α , 35 mA, 20 kV). UV-visible diffuse reflectance spectra of the powders were recorded in order to determine the band gaps (Varian Model DMS300 spectrometer, scan rate: 200 nm/min). Methanol (J.T. Baker) and silver nitrate (Johnson Matthey) were used without further purification as reducing or oxidizing reagents for hydrogen and oxygen evolution. In hydrogen evolution experiments, aqueous H_2PtCl_6 solution (1 wt% as Pt) was added to the oxide suspension. Under such conditions, an active catalyst will cause photodeposition of Pt on the surface of the metal oxide [10], producing a metal island capable of acting as a hydrogen evolution site.

The photocatalytic reactions were carried out in a closed gas circulation system equipped with a vacuum line and a gas chromatography sampling inlet [11]. The catalyst was dispersed in the solution by sonication prior to the reaction. A mixture of the catalyst (0.3 g) and the aqueous solution (80 mL) was stirred magnetically in a reaction cell equipped with an optically flat Pyrex window and degassed at least 30 min by vacuum evacuation. After degassing and adding 100 Torr of Ar, we irradiated the suspension using a high pressure mercury lamp (Ushio, USH = 205, DPA, 200 W). The amount of hydrogen and oxygen evolved were determined by gas chromatography (Varian Model 90-P, Ar carrier, molecular sieve 5A column, thermal conductivity detector).

3. Results and discussion

The observed catalytic activities for hydrogen and oxygen evolution of four ternary lead oxides, MoO_3 , and TiO_2 are presented in table 1. Only PbMoO_4 and TiO_2 show appreciable photoactivity. The activity for oxygen evolution on the

Table 1

Photocatalytic activity of several ternary and binary metal oxides H₂ and O₂ evolutions from aqueous solution.

Catalyst ^a	Evolved gas (μmol) ^b	
	H ₂ ^c	O ₂ ^d
PbCrO ₄	0	0
PbMoO ₄	59	97
PbWO ₄	0	0
PbO	0	0
MoO ₃	0	0
TiO ₂	477	120

^a 0.3 g in 80 mL solution; ^b reaction time: 2 h, light source: 200 W high pressure Hg lamp; ^c from aq. CH₃OH (90:10 H₂O:MeOH, 80 mL), H₂PtCl₆ (1 wt% Pt) was added; ^d from aq. AgNO₃ (0.01 M, 80 mL).

PbMoO₄ powder was reproducibly comparable to that observed on TiO₂, but the activity for hydrogen evolution was significantly lower. In the discussion which follows, we assume that methanol is oxidized and dihydrogen evolves from water when aqueous methanol solutions are irradiated, and that Ag⁺ is reduced and oxygen evolves from water when aqueous silver nitrate solutions are irradiated.

Platinum deposition was indispensable for the hydrogen evolution on PbMoO₄ powder. The irradiation of Pt-free PbMoO₄ suspended in distilled water produced no hydrogen and only small amounts of oxygen (6 μmol after 2 h); simultaneously the color changed from light yellow to dark brown, suggesting that PbMoO₄ itself was reduced. This accounts for the absence of hydrogen evolution and presumably results from the lack of hydrogen evolution sites on the surface of native PbMoO₄.

In contrast, PbO and MoO₃ show no activity. These materials probably fail to photocatalyze hydrogen evolution because their conduction band edges are not sufficiently negative (compared with the potential required for water reduction). When MoO₃ was irradiated in aqueous methanol solution, its color turned to deep blue, as would be consistent with metal oxide reduction. Thus, the photooxidation of methanol proceeds on MoO₃, but evolution of dioxygen does not. When PbO powder is irradiated in aqueous silver nitrate, silver is photodeposited, judging from the change of the color (from yellow to grey). In this case, PbO is probably oxidized to either Pb(III) or Pb(IV) at the expense of oxygen evolution [2].

The time course of hydrogen and oxygen evolution on Pt/PbMoO₄ and PbMoO₄ is shown in fig. 1. The oxygen evolution rate is relatively constant, although it ultimately decreased gradually with time because of the deposition of Ag metal in the surface, the change of pH, etc. Photocatalyzed hydrogen evolution stopped after 2 h.

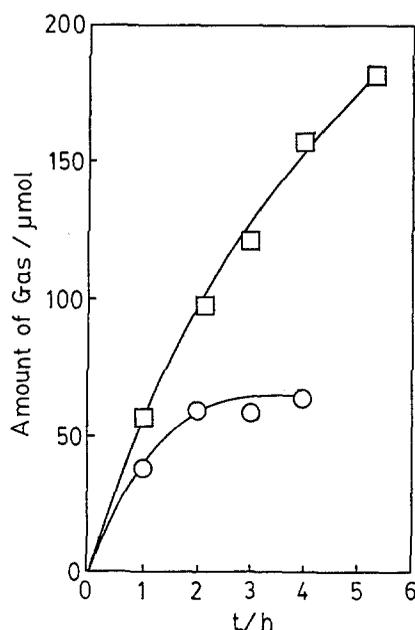


Fig. 1. H₂ evolution from aqueous CH₃OH and O₂ evolution from aqueous AgNO₃ solutions. Open circles: H₂ from aq. CH₃OH over Pt (1 wt%)/PbMoO₄. Open squares: O₂ from aq. AgNO₃ over PbMoO₃. In both cases, 0.3 g of catalyst was used and the light source was a 200 W high pressure Hg lamp.

In photocatalytic reaction research, the moles of evolved gas should always be compared with the moles of catalyst. In this study, PbMoO₄ (0.3 g or 820 μmol) was used. Since 4h⁺ (holes) are required for each molecule of O₂ produced, 720 μmol of holes are needed to evolve 180 μmol of oxygen (after 5 h), while 120 μmol of electrons are needed to form 60 μmol of hydrogen (after 4 h) from fig. 1. Based on these values and the fact that oxygen evolution shows no signs of diminishing, we conclude that oxygen evolves photocatalytically. The situation for hydrogen evolution is unclear.

Diffuse reflectance spectra of PbCrO₄, PbMoO₄, and PbWO₄ powders are shown in fig. 2. The band gaps of PbCrO₄, PbMoO₄, and PbWO₄ powders were estimated to be 2.2, 3.2, and 3.8 eV respectively. Band gap excitation of PbMoO₄, which showed significant photocatalytic activity in this study, should occur via the electron transfer from the valence band (electron density localized at Pb²⁺) to the conduction band (localized in MoO₄²⁻) [12].

Both PbMoO₄ and PbWO₄, which have a Scheelite structure, have been studied as photoconductors [13]. Only PbMoO₄ showed appreciable photocatalytic activity, despite its photophysical similarity to PbWO₄. The reason is unclear. One factor tending to reduce the measured activity is the larger band gap (3.8 eV), which is smaller than but comparable to the optical cut-off of Pyrex (~ 4 eV). This factor alone cannot account for the absence of activity, so subtle electronic/

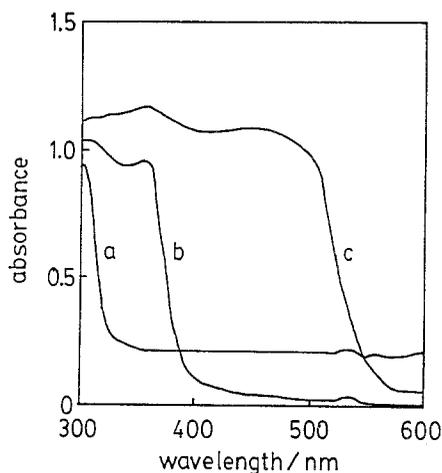


Fig. 2. Diffuse reflectance spectra of (a) PbWO_4 , (b) PbMoO_4 , and (c) PbCrO_4 powders.

chemical factors must be important. PbCrO_4 did not show photoactivity, despite its small band gap (2.2 eV). Perhaps recombination between electrons and holes is too fast to allow interfacial electron transfer at the photocatalyst surface to compete. As for PbWO_4 , the absence of active sites on the surface is another possible explanation.

4. Summary

Following the empirical observation that photocatalytic activity of oxides occurs along certain diagonals of the periodic table (for the cation); we tested a set of ternary Pb-IVB-oxygen compounds - PbO , PbCrO_4 , PbMoO_4 , and PbWO_4 . Of these, only PbMoO_4 shows any photoactivity for sacrificial water decomposition. Platinized PbMoO_4 was photoactive for dihydrogen evolution from Ag^+ -containing water solutions. The activity for dioxygen evolution was comparable to TiO_2 . Thus, PbMoO_4 emerges as a new material showing competitive photoactivity.

Acknowledgment

Support of this work by the Gas Research Institute is gratefully acknowledged.

References

- [1] M. Gratzel, In: *Energy Resources through Photochemistry and Catalysis* (Academic Press Inc., New York, 1983).

- [2] K.L. Hardee and A.J. Bard, *J. Electrochem. Soc.* 124 (1977) 215.
- [3] H.H. Kung, H.S. Jarrett, A.W. Sleight and A.J. Ferretti, *J. Appl. Phys.* 48 (1977) 2463.
- [4] D.E. Scaife, *Solar Energy* 24 (1980) 41.
- [5] W. Mindt, *J. Electrochem. Soc.*, 116 (1969) 1077.
- [6] L.C. Schumacher, I.B. Holzheter and M.J. Dignam, *J. Electroanal. Chem.* 261 (1989) 331.
- [7] G.H. Brilmyer, in: *Advances in Lead Batteries*, eds. K. Bullock and D. Pavlov (Electrochem. Soc., Pennington, NJ (1984) (Proceedings Vol. 84-14) pp 142-153.
- [8] D. Pavlov, S. Zanova and G. Papozov, *J. Electrochem. Soc.* 124 (1977) 152.
- [9] D. Pavlov, *J. Electroanal. Chem.* 118 (1981) 167.
- [10] B. Krauetler and A.J. Bard, *J. Am. Chem. Soc.* 100 (1978) 2239.
- [11] K. Domen, A. Kudo and T. Onishi, *J. Catal.* 102 (1986) 99.
- [12] M. Bohn, O. Erb and A. Scharmann, *Phys. Stat. Sol.* 84 (1984) 291.
- [13] W.V. Loo, *Phys. Stat. Sol.* 27 (1975) 565.
- [14] M. Shibata, A. Kudo, A. Tanaka, K. Domen, K. Maruya and T. Onishi, *Chem. Lett.* (1987) 1017.